

# Fermi surface topology and vortex state in MgB<sub>2</sub>

T. Dahm <sup>\*</sup>, S. Graser, and N. Schopohl

*Institut für Theoretische Physik, Universität Tübingen, Auf der Morgenstelle 14, D-72076 Tübingen, Germany*

## Abstract

Based on a detailed modeling of the Fermi surface topology of MgB<sub>2</sub> we calculated the anisotropy of the upper critical field  $B_{c2}$  within the two gap model. The  $\sigma$ -band is modeled as a distorted cylinder and the  $\pi$ -band as a half-torus, with parameters determined from bandstructure calculations. Our results show that the unusual strong temperature dependence of the  $B_{c2}$  anisotropy, that has been observed recently, can be understood due to the small c-axis dispersion of the cylindrical Fermi surface sheets and the small interband pairing interaction as obtained from bandstructure calculations. We calculate the magnetic field dependence of the density of states within the vortex state for field in c-axis direction and compare with recent measurements of the specific heat on MgB<sub>2</sub> single crystals.

*Key words:* Magnesium diboride, upper critical field, vortex state, specific heat  
*PACS:* 74.20.-z, 74.25.Op, 74.70.Ad

It now appears widely accepted that the superconducting state of MgB<sub>2</sub> has to be described by two different *s*-wave gaps [1]. This also implies unusual behavior in its vortex state, which has been observed recently. The anisotropy of the upper critical field  $B_{c2}$  displays an anomalous strong temperature dependence. An upward curvature of  $B_{c2}$  close to  $T_c$  is observed, when the field is directed in ab-plane direction [2,3]. The specific heat and thermal conductivity show a rapid increase as a function of magnetic field [4,5] and the size of the vortex core and local density of states show unusual behavior as well [6]. While it seems reasonable that these observations are related to the two-gap nature of MgB<sub>2</sub>, a detailed understanding of all of these phenomena within a single model is still lacking. We have shown recently that the unusual behavior of the upper critical field can be understood, if the topology of the Fermi surface and the weak interband pairing interaction is taken into account [7]. Within our model the  $\sigma$ -band is described as a distorted cylinder and the  $\pi$ -band as a half-torus, in close agreement with bandstructure calculations. In Fig. 1 we present a direct comparison of the  $B_{c2}$  data by Lyard et al [3] with our calculation for

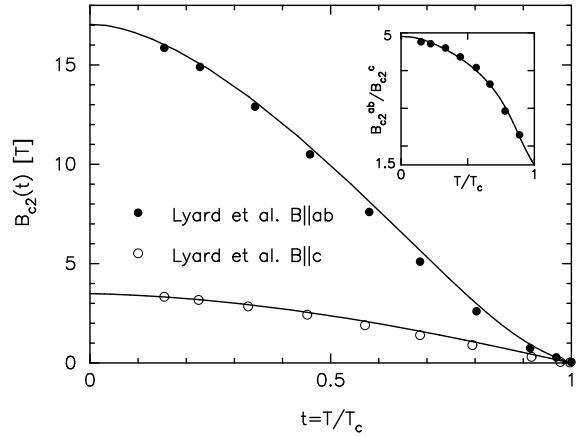


Fig. 1. Upper critical field as a function of temperature for field in c-axis and ab-plane direction. Comparison with Lyard et al. [3] (symbols). The inset shows the strong temperature dependence of the anisotropy ratio  $B_{c2}^{ab}/B_{c2}^c$ .

interband pairing strength  $\eta = 0.121$  and c-axis dispersion  $\epsilon_c = 0.182$  of the cylindrical Fermi surface sheet as described in Ref. [7]. For field in c-axis direction the temperature dependence follows very much a conventional one-band temperature dependence [8]. However,

<sup>\*</sup> Corresponding author. e-mail: dahm@uni-tuebingen.de

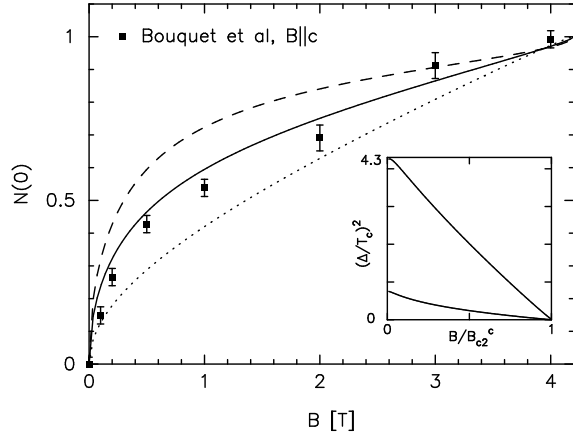


Fig. 2. Zero energy density of states as a function of magnetic field in  $c$ -axis direction (solid line) and comparison with results from specific heat measurements by Bouquet et al. [4] (symbols) on MgB<sub>2</sub> single crystals taking  $B_{c2}^c = 4.2$  T. The inset shows the field dependence of  $(\Delta/T_c)^2$  for the two gaps.

a clear upward curvature close to  $T_c$  is obtained for field in  $ab$ -plane direction. This results from a strong temperature dependence of the distortion of the vortex lattice, which at low temperatures is dominated by the  $\sigma$ -band, while close to  $T_c$  both bands contribute equally [7].

Since our model offers a good description of  $B_{c2}$  in MgB<sub>2</sub> we extended our calculations now to magnetic fields below  $B_{c2}$  using the analytical method described in Ref. [9] for the calculation of the density of states within the vortex state. Within this method the field dependence of the partial density of states of each band at the Fermi level for field in  $c$ -axis direction is given by

$$N_\alpha(\omega = 0, B) = \left\langle \frac{N_\alpha(0)}{\sqrt{1 + \frac{4\Phi_0 \Delta_\alpha^2(B)}{\pi \hbar^2 B v_{F,\alpha,ab}^2}}} \right\rangle_\alpha \quad (1)$$

Here,  $v_{F,\alpha,ab}$  is the  $ab$ -plane component of the Fermi velocity of band  $\alpha \in \{\sigma, \pi\}$ .  $N_\alpha(0)$  is the normal state density of states,  $\Phi_0$  the flux quantum, and  $\langle \dots \rangle_\alpha$  denotes a Fermi surface average over band  $\alpha$ . For the cylindrical and torus Fermi surfaces considered here these averages can be done analytically. The field dependence of the gap  $\Delta_\alpha(B)$  is obtained from a solution of the two by two gap equation in the vortex state [9].

In Fig. 2 we show the magnetic field dependence of the total density of states at the Fermi level (solid line) for the same set of parameters as in Fig. 1 showing fair agreement with the specific heat data of Bouquet et al. [4]. While the contribution from the large gap ( $\sigma$  band, dotted line) to a good approximation follows the behavior of a single band  $s$ -wave superconductor, the contribution from the small gap ( $\pi$  band, dashed line) displays a rapid increase. The inset shows the field dependence of the square of the two gaps. It shows that

the square of the large gap to a very good approximation is a linear function of the magnetic field, while the small gap shows some reduction at higher fields. If we nevertheless approximate the squares of the gaps as linear functions in  $B/B_{c2}^c$  we find the following useful analytical expressions:

$$N_\sigma(B) \approx \left[ 1 + 0.36 \frac{\Delta_\sigma^2(0)}{T_c^2} \left( \frac{B_{c2}^c}{B} - 1 \right) \right]^{-1/2}$$

and

$$N_\pi(B) = \frac{2}{\pi - 2\kappa} \left[ \arcsin k - \frac{\kappa}{k} E(k) - \kappa \frac{1 - k^2}{k} K(k) \right]$$

$$\text{with } k(B) \approx \left[ 1 + 0.36 \frac{\Delta_\pi^2(0)}{T_c^2} \frac{v_{F,\pi}^2}{v_{F,\sigma}^2} \left( \frac{B_{c2}^c}{B} - 1 \right) \right]^{-1/2}.$$

Here,  $E(k)$  and  $K(k)$  are the complete elliptical integrals and  $\kappa = 0.25$  the ratio of the two radii of the torus Fermi surface as defined in Ref. [7]. At low magnetic fields from Eq. (1) we can obtain the following limiting expressions:  $N_\sigma(B) \approx 1.67 \frac{T_c}{\Delta_\sigma(0)} \sqrt{\frac{B}{B_{c2}^c}}$

and  $N_\pi(B) \approx 1.01 \frac{T_c}{\Delta_\pi(0)} \frac{v_{F,\pi}}{v_{F,\sigma}} \sqrt{\frac{B}{B_{c2}^c}}$ . These expressions show that the rapid increase of the density of states of the  $\pi$ -band is due to two reasons: the small value of  $\Delta_\pi(0)/T_c$  and the higher in-plane Fermi velocity of the  $\pi$ -band and thus has a different physical origin than the  $d$ -wave behavior known as Volovik's law [10]. We note, however, that these analytical expressions are only valid for field directed into  $c$ -axis direction. For other field directions the distortion of the vortex lattice has to be taken into account and we find important modifications. Details will be published elsewhere [11].

## References

- [1] P. C. Canfield and G. W. Crabtree, *Physics Today* **56**, No. 3, p. 34 (2003).
- [2] M. Angst et al, *Phys. Rev. Lett.* **88**, 167004 (2002).
- [3] L. Lyard et al, *Phys. Rev. B* **66**, 180502(R) (2002).
- [4] F. Bouquet et al, *Phys. Rev. Lett.* **89**, 257001 (2002).
- [5] A. V. Sologubenko et al, *Phys. Rev. B* **66**, 014504 (2002).
- [6] M. R. Eskildsen et al, *Phys. Rev. Lett.* **89**, 187003 (2002).
- [7] T. Dahm and N. Schopohl, *cond-mat/0212188*.
- [8] A. I. Posazhennikova, T. Dahm, and K. Maki, *Europhys. Lett.* **60**, 134 (2002).
- [9] T. Dahm, S. Graser, C. Iniotakis, and N. Schopohl, *Phys. Rev. B* **66**, 144515 (2002).
- [10] G. E. Volovik, *JETP Lett.* **58**, 469 (1993).
- [11] T. Dahm, S. Graser, and N. Schopohl, unpublished.